

Parametric Study on the Properties of Geopolymer Mortar Incorporating Bottom Ash

Djwantoro Hardjito^C and Shaw Shen Fung

*Dept. of Civil and Construction Engineering, School of Engineering and Science
Curtin University of Technology, Sarawak, MALAYSIA*

Selected paper from the Asia Pacific Structural Engineering Conference, APSEC 2009

Abstract

This paper presents the results of study on effect of various parameters on mechanical properties of fly ash-based geopolymer mortar with bottom ash as partial or full replacement for sand. Compressive strength of samples with 10% bottom ash (BA) was comparable to those with only sand. Further increase in bottom ash content decreased the compressive strength. However, the reverse tendency occurred after exposing the samples to 1000oC for 24 hours.

Keywords: Fly ash, bottom ash; geopolymer mortar; compressive strength; thermal exposure; workability

1. Introduction

Portland cement is widely used in concrete industry since many decades ago, however it releases green house gases, i.e. carbon dioxide (CO₂), into the atmosphere during its manufacture [1]. Geopolymer technology is one of the new technologies attempted to reduce the use of Portland cement in concrete. Fly ash reacts with alkaline solutions to form a cementitious material; fly ash based geopolymer; which does not emit carbon dioxide into the atmosphere. In this project, bottom ash is considered as partial- or full-replacement for sand as fine aggregate in the geopolymer mortar. To date, bottom ash from Sejingkat Coal Fired Power Station in Kuching, Sarawak, Malaysia, has not been utilised yet.

Fly ash and bottom ash are residues from the combustion of coal. Fly ash is captured in the chimney while bottom ash is collected from the bottom of the furnace from the coal fired power plant. Furthermore, the particles of fly ash are very fine whereas bottom ash has much larger particle size, which is about the size of sand but more porous. In Sejingkat Coal Fired Power Station, fly ash and bottom ash are disposed off into an 81,000 m² area, 2.4 m deep ash pond situated beside the power station [2]. In fact, currently there are two ash ponds with one of them has been fully utilized.

Fly ash based geopolymer with bottom ash gives emphasis in reducing carbon dioxide emission and in recycling fly ash and bottom ash. Since fly ash and bottom ash are the waste products of coal fired power plant, this research can lead to the awareness of sustainable

^C Corresponding author Email: Djwantoro Hardjito

Email: djwantoro.h@curtin.edu.my

© 2009-2012 All rights reserved. ISSR Journals

development to the society. This is very advisable in sustainable developments to reduce CO₂ emission and to recycle the waste materials. At present time, there is limited information on the influence of parameters on geopolymer available, especially geopolymer with bottom ash as the fine aggregate. As a result, study on the effect of different parameters on the fly ash based geopolymer with bottom ash as sand replacement is needed. In addition, this research can provide additional information and to further introduce geopolymer to concrete industry.

2. Literature Review

Geopolymers are amorphous to semi-crystalline three-dimensional aluminosilicate polymers similar to zeolites. Geopolymers consist of polymeric silicon-oxygen-aluminium framework with silicon and aluminium tetrahedral alternately linked together in three direction by sharing all the oxygen atoms. The negative charge created by aluminium is balanced by the presence of positive ions such as Na⁺, K⁺, and Ca⁺. The empirical formula of these mineral polymers is $M_n[-(\text{SiO}_2)_z-\text{AlO}_2]_n \cdot w\text{H}_2\text{O}$, where M is an alkali cation such as potassium or sodium, the symbol - indicates the presence of a bond, z is 1, 2 or 3, and n is the degree of polymerisation [3].

Geopolymer with fluidized bed combustion bottom ash (FBC-BA) experienced a decrease in compressive strength with the increase of the content of FBC-BA in the prepared specimens. Increasing the content of FBC-BA to about 50% caused the decrease of the compressive strength [4].

For the case of normal fly ash concrete incorporating bottom ash as replacement for fly ash, the increase in bottom ash content decreased the compressive strength. Furthermore, most of the compressive strengths were gained after 28 days. The pozzolanic reactivity of bottom ash could be improved with adequate grinding and use it as sand replacement in concrete, where sand is more expensive than bottom ash [5].

Water retainability is defined as the amount of water absorbed into the pores and adsorbed on the rough surface of bottom ash. The usual collapsed-cone test method to determine the saturated surface dry condition was not achievable for bottom ash. Therefore an alternative method based on the gravitational removal of excess water from the bottom ash was introduced to determine the water retainability of bottom ash [6].

The compressive strength of fly ash-based geopolymer mortar exposed to 400 °C increased by about 100% compared to samples without any exposure to high thermal environment. Geopolymer possesses high thermal resistance up to 800 °C without showing any decrease in compressive strength [2]. However, after exposure to thermal exposure above 800 °C, compressive strength of geopolymer prepared using sodium based alkaline activator rapidly declined [7]. In fact, geopolymer mortar does not experience release water in an explosive manner or dehydrate to a powder like OPC. In brief, geopolymer mortar is able to resist thermal exposure up to 1000 °C [8].

3. Materials and Experimental Details

3.1 Materials

Fly ash, Class F under ASTM C 618, used in this experiment was obtained from Sejingkat Coal-Fired Power Station. The coal used in the power station is mainly supplied from the coal mine in Merit Pila, Kapit, Sarawak, Malaysia. Specific surface area and particle density of the fly ash are 1.51 m²/ml and 2370 kg/m³ respectively. The chemical composition of the fly ash, as determined by X-Ray Fluorescence (XRF) analysis is shown in Table 1. According to the chemical composition as shown in Table 1, the mass ratio of SiO₂ to Al₂O₃ of the fly ash is 2.34.

Similarly, bottom ash used in this experiment was obtained from Sejingkat Coal-Fired Power Station. The specific gravity of the bottom ash is 2.23 and fineness modulus

(FM) is 0.14. Suitable moisture content (22%) of bottom ash was prepared in advance and stored for prior use. Sand used in this experiment is in saturated surface-dry (SSD) condition. Fineness modulus (FM) and specific gravity are 1.44 and 2.67 respectively. These data reveal that the particle size of the sand is rather small with FM only 1.44, moreover the particle size of the bottom ash is even smaller than sand (FM of 0.14).

Mixture of Potassium Silicate (K_2SiO_3) solution and Potassium Hydroxide (KOH) solution were chosen as the alkaline activator. This was because the type of alkaline activator that contained only hydroxides revealed in a lower reaction rate than when soluble silicates were also used as the activators [9]. Furthermore, potassium-based activator was chosen because it produced a better strength compared to sodium-based activator [10].

TABLE 1 : CHEMICAL COMPOSITION OF FLY ASH AS DETERMINED BY XRF

Oxides	% mass	Oxides
SiO ₂	58.0	SiO ₂
Al ₂ O ₃	24.8	Al ₂ O ₃
Fe ₂ O ₃	7.17	Fe ₂ O ₃
K ₂ O	3.14	K ₂ O
CaO	2.40	CaO
MgO	1.95	MgO
TiO ₂	1.05	TiO ₂
P ₂ O ₅	0.34	P ₂ O ₅
Na ₂ O	0.30	Na ₂ O

3.2 Fire Resistance Tests

In order to analyse the effect of content of bottom ash on compressive strength, R1 was chosen as the reference sample. On the other hand, R2 was chosen as the reference sample in the experiment on the effect of different curing temperature, concentration of KOH solution and K_2SiO_3 -to-KOH solution ratio by mass on compressive strength.

Furthermore, mixtures R1, R2, 1-7, 12, 13, 15 and 17 were subjected to thermal exposure of 400 °C, 700 °C and 1000 °C on the sixth day and compressive strength test was conducted on the next day. Seventh days compressive strength of samples with no thermal exposure was taken as the reference for the compressive strength of samples subjected to thermal exposure. The experimental programme is shown in Table 2.

Fine aggregate to fly ash ratio by mass of 2.75 was attempted to design the required quantity of all geopolymer mortars [11]. Besides that, K_2SiO_3 solution and KOH solution were weighted according to the required proportion. The mixture proportion is shown in Table 3.

3.3 Mixing, Casting, Curing and Thermal Exposure

The mixing and casting of the geopolymer mortar was referred to method implemented by Tsen [2]. Raw materials, i.e. fly ash and fine aggregate, were dry mixed in the mixer at the paddle speed of 140 ± 5 r/min for 2 minutes. At the same time, alkaline activator with mixture of K_2SiO_3 solution and KOH solution were premixed in another flask. After that, the alkaline activator was mixed with the raw materials in the mixer for another 10 minutes.

Then, the fresh geopolymer mortar was placed in the 50 mm x 50 mm x 50 mm specimen moulds in two layers. Each layer was compacted by a tamper for 20 times. After the casting of the geopolymer mortars in the specimen moulds, the mixtures were vibrated using vibrating table for another 2 minutes to remove air voids. All the mixing and casting were done in an air-conditioned room of temperature approximately at 25 °C.

Next, all the mixtures were cured in an oven without delay time at the specific curing temperature for 24 hours. Samples were demoulded after the curing process in the oven and cured in room temperature until the testing age.

Samples that subjected to thermal exposure were exposed in a furnace on the sixth day at an incremental rate of 10 °C/min from room temperature. The desired temperature was maintained for 3 hours before the samples were allowed to cool naturally to room temperature in the furnace. Then the samples were tested on the next day.

TABLE 2 : EXPERIMENTAL PROGRAMME

Mixture No.	Curing Temp (°C)	Conc. of KOH (M)	K ₂ SiO ₃ -to-KOH Ratio by Mass	Bottom Ash Content (%)	Sand Content (%)
R1	60	12	1.0	0	100
R2	60	12	1.0	10	90
1	50	12	1.0	10	90
2	70	12	1.0	10	90
3	80	12	1.0	10	90
4	60	6	1.0	10	90
5	60	8	1.0	10	90
6	60	10	1.0	10	90
7	60	14	1.0	10	90
8*	60	12	0.4	10	90
9*	60	12	0.8	10	90
10*	60	12	1.5	10	90
11*	60	12	2.5	10	90
12	60	12	1.0	25	75
13	60	12	1.0	50	50
14*	60	12	1.0	65	35
15	60	12	1.0	75	25
16*	60	12	1.0	90	10
17	60	12	1.0	100	0

*Mixtures do not subject to thermal exposure.

TABLE 3 : MIXTURE PROPORTION

Mixture No.	Fine Aggregate		Fly Ash (kg/m ³)	K ₂ SiO ₃ (kg/m ³)	KOH (kg/m ³)
	Bottom Ash (kg/m ³)	Sand (kg/m ³)			
R1	0	1382	503	127.5	127.5
R2	138	1244	503	127.5	127.5
1	138	1244	503	127.5	127.5
2	138	1244	503	127.5	127.5
3	138	1244	503	127.5	127.5
4	138	1244	503	127.5	127.5
5	138	1244	503	127.5	127.5
6	138	1244	503	127.5	127.5
7	138	1244	503	127.5	127.5
8*	138	1244	503	72.9	182.1
9*	138	1244	503	113.3	141.7
10*	138	1244	503	153.0	102.0
11*	138	1244	503	182.1	72.9
12	346	1036	503	127.5	127.5
13	691	691	503	127.5	127.5
14*	898	484	503	127.5	127.5
15	1036	346	503	127.5	127.5
16*	1244	138	503	127.5	127.5
17	1382	0	503	127.5	127.5

*Mixtures do not subject to thermal exposure.

3.4 Testing

Three 50 mm x 50 mm x 50 mm samples were tested for each data. Load rate 90 kN/min was applied on the sample. The maximum load shown by the testing machine was recorded and the compressive strength of the sample was calculated.

Workability was measured by the flow of the fresh geopolymer mortar on flow table for mortar. First, flow mould was placed in the middle of the flow table. A layer of fresh geopolymer mortar about 25 mm thick was placed in the mould and tamped with the tampers for 20 times. This was repeated for the second layer. Then the mould was lifted away and immediately the table was dropped from a height of 12.7 ± 0.13 mm for 25 times in 15 sec. Finally, the diameter of the geopolymer mortar along the four lines scribed in the table top was recorded. Then, the flow expressed as a percentage of the original base diameter was calculated as follow. First, 'A', the average of the four readings, in millimeters, minus the original inside base diameter was calculated. Next, 'A' was divided by the original inside base diameter and multiplied by 100.

4. Results and Discussion

3.1 Compressive Strength

(1) Content of Bottom Ash

Mixture R1, R2, 12-17 were made to investigate the effect of content of bottom ash on compressive strength and figure 1 shows the results. The compressive strength of the bottom ash geopolymer mortar decreases with the increase of bottom ash content. This could, probably, be due to the water released into the mixture by the bottom ash [12]. Water can be highly retained, in term of absorption and adsorption, into and onto the bottom ash due to the high porosity and irregular surface [6]. With the amount of the water increased in the mortar, the compressive strength of the geopolymer mortar eventually decreases. On the other hand, the higher porosity of the bottom ash also caused the lower compressive strength to the geopolymer mortar [13]. However, 10% of river sand can be replaced by bottom ash as fine aggregates in fly ash-based geopolymer mortar without any significant decrease in its compressive strength.

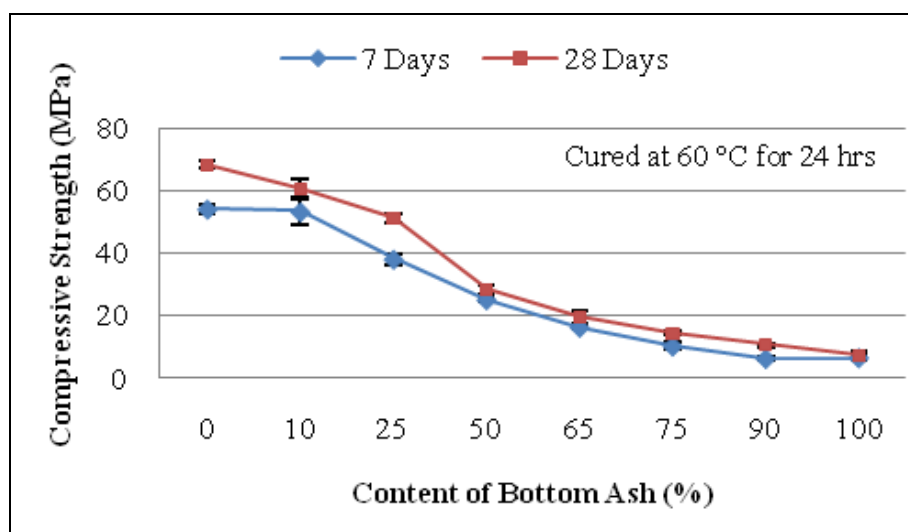


Figure 1. Effect of Content of Bottom Ash on Compressive Strength

(2) Curing Temperature

Mixture R2 and 1-3 were made to analyze the effect of curing temperature on compressive strength and figure 2 shows the results. A higher curing temperature will increase the compressive strength of the geopolymer mortar. This is because energy required for dissolution of fly ash is an endothermic process [14]. However, the samples will normally experience the loss of moisture content with high curing temperature whereby geopolymerisation requires the presence of moisture to achieve a good compressive strength [11].

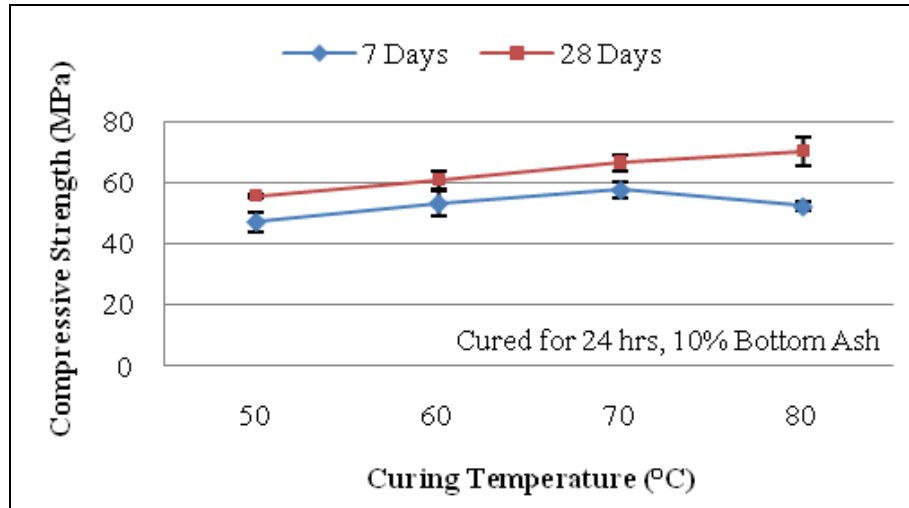


Figure 2. Effect of Curing Temperature on Compressive Strength

(3) Concentration of KOH Solution

Mixture R2 and 4-7 were made to study the effect of concentration of KOH solution on compressive strength and Fig. 3 shows the results. The higher the concentration of the KOH solution, the higher the compressive strength is. This is mainly because the concentration of KOH solution is directly affecting the dissolution of fly ash which affects the formation of the geopolymer framework [15]. However, the compressive strength resulted in this research is slightly lower than compressive strength in research conducted by Tsen [2]. This is most probably due to the incorporation of bottom ash in the sample.

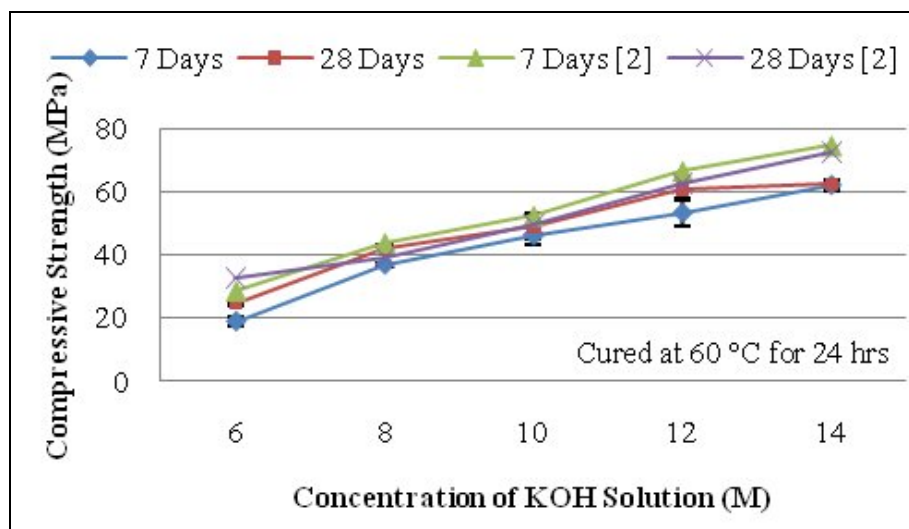


Figure 3. Effect of Concentration of KOH Solution on Compressive Strength

(4) K₂SiO₃-to-KOH Solution Ratio by Mass

Mixture R2 and 8-11 were made to study the effect of K₂SiO₃-to-KOH solution ratio by mass on compressive strength and figure 4 shows the results. Compressive strength of samples with K₂SiO₃-to-KOH solution ratio by mass of 0.4 to 1.0 are noticeably higher than those with K₂SiO₃-to-KOH solution ratio by mass of 1.5 and 2.5 which is similar to research by Tsen [2]. Again, similar to this researcher's research, the optimum K₂SiO₃-to-KOH solution ratio by mass for compressive strength was 1.0. However, this was rather unexpected. In research conducted by Hardjito et al. [16] on the low calcium fly ash reacted by sodium based alkaline solution showed that the higher of silicate-to-hydroxide solution ratio by mass resulted in higher compressive strength.

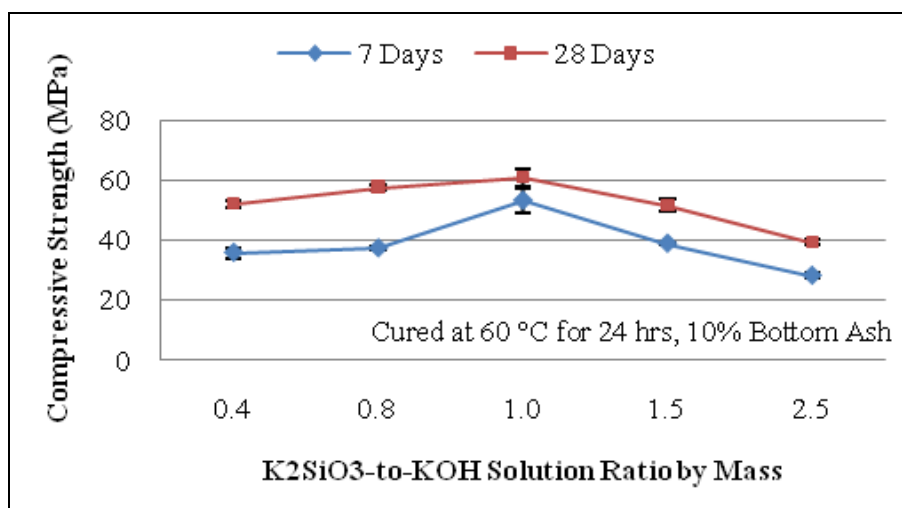


Figure 4. Effect of K₂SiO₃-to-KOH Solution Ratio by Mass on Compressive Strength

4.2. Thermal Resistance

Mixture R1, R2, 12, 13, 15 and 17 were made to study the effect of content of bottom ash on compressive strength. From figure 5, the highest compressive strength is achieved by the samples exposed to 400 °C which also shown in Tsen [2] report. Geopolymer possesses high thermal resistance up to 700 °C without any significant decrease in compressive strength. Furthermore, samples exposed to 1000 °C is experiencing decrease in compressive strength as reported also by other researcher [7]. In fact, similar to other researcher, these samples do not experience release water in an explosive manner or dehydrate to a powder like OPC [8].

The compressive strength increases with the increase of bottom ash content in samples exposed to 1000 °C. Undeniable, this trend is different compared to the samples that are not exposed to any high thermal environment or exposed to temperature lower than 700 °C which can be observed from Fig. 5. In brief, samples with lower bottom ash content (0%-25%) decreases in compressive strength after exposure to elevated temperature of 400 °C to 1000 °C, meanwhile samples with higher bottom ash content (50%-100%) increases in compressive strength after exposure to elevated temperature of 400 °C to 1000 °C which can be observed from Fig. 6. This is probably due to higher temperature, especially at 1000 °C, activated the bottom ash, and indeed increased the compressive strength of the samples. Thus, further research on the characteristic of bottom ash in high temperature is needed.

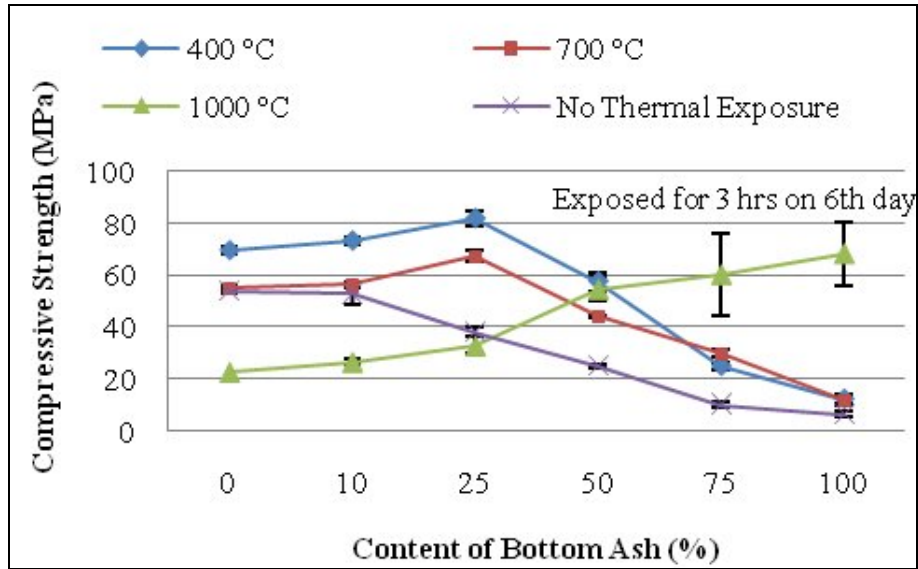


Figure 5. Effect of Content of Bottom Ash on Compressive Strength after Thermal Exposure

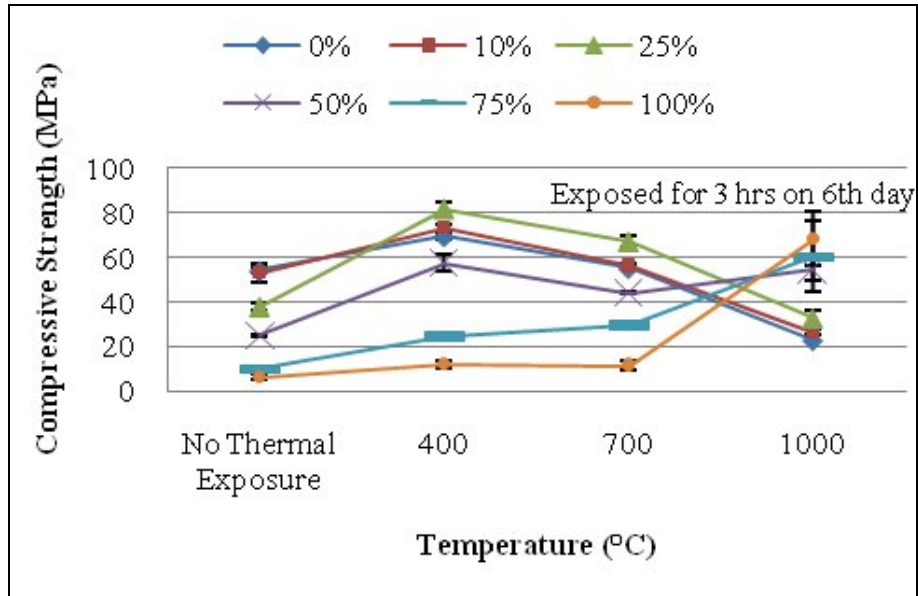


Figure 6. Effect of Thermal Exposure on Compressive Strength

4.3. Workability

Workability of fresh geopolymer mortar of mixture R1, R2 and 12-17 were studied in this section. Effect of bottom ash content on workability is shown in figure 7. First, workability measured by flow of fresh geopolymer mortar increases with the increase of bottom ash content in the mixture. This is because water retained by the bottom ash will be released into the mixture during the mixing [12]. This additional water will increase the workability of the fresh mortar. However, with the amount of bottom ash in fresh geopolymer mortar more than 75%, workability decreases. This is most probably due to the angular shape and rough texture causing high inter-particle friction of the bottom ash although the water content increased in the mixture [6]. The more the content of bottom ash in fresh mortar, the higher the inter-particle friction is.

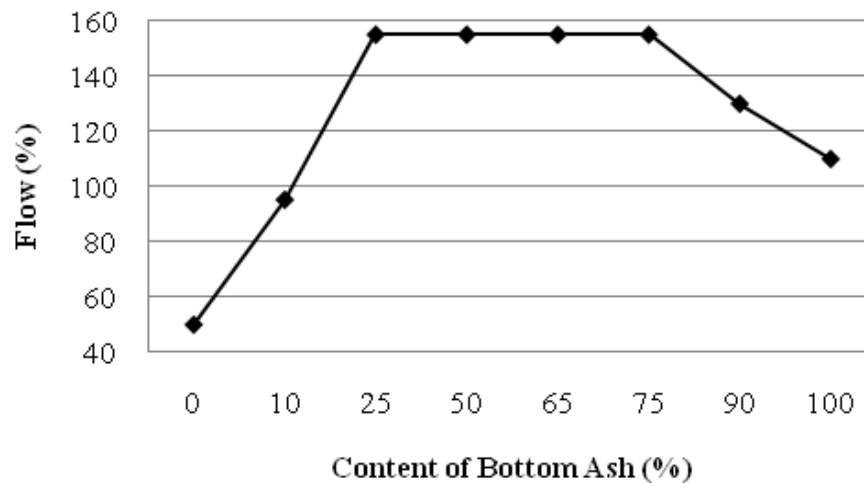


Figure 7. Effect of Content of Bottom Ash on Workability

5. Conclusion

1. Increase of bottom ash content decreases the compressive strength of geopolymer mortar. However, compressive strength of geopolymer mortar with 10% of bottom ash is comparable to geopolymer mortar without bottom ash.
2. Increase of curing temperature increases the compressive strength of the geopolymer mortar.
3. Increase in concentration of KOH solution also increases the compressive strength of geopolymer mortar.
4. The optimum K_2SiO_3 -to-KOH solution ratio by mass is about 1.0.
5. Geopolymer mortar with lower bottom ash content (0%-25%) decreases in compressive strength after exposure to elevated temperature from 400 °C to 1000 °C, meanwhile geopolymer mortar with higher bottom ash content (50%-100%) increases in compressive strength after exposure to elevated temperature of 400 °C to 1000 °C.
6. Increase of bottom ash content increases workability of fresh geopolymer mortar but it decreases with bottom ash content more than 75%.

References

- [1] Malhotra, V.M., " Introduction: Sustainable Development and Concrete Technology", *Concrete International* Vol. 24, No. 7, 2002b, pp. 22.
- [2] Tsen, M.Z., "The properties of fly ash-based geopolymer mortar with potassium-based alkaline reactor": Curtin University of Technology 2008.
- [3] Davidovits, J., " High-Alkali Cements for 21st Century Concretes", *Special Publication* Vol. 144, 1994, pp. 383-398.
- [4] Slavik, R., V. Bednarik, M. Vondruska, and A. Nemecek, " Preparation of geopolymer from fluidized bed combustion bottom ash", *Journal of Materials Processing Technology* Vol. 200, No. 1-3, 2008, pp. 265-270.
- [5] Kula, I., A. Olgun, Y. Erdogan, and V. Sevinc, " Effects of colemanite waste, cool bottom ash, and fly ash on the properties of cement", *Cement and Concrete Research* Vol. 31, No. 3, 2001, pp. 491-494.
- [6] Kasemchaisiri, R., and S. Tangtermsirikul, " A method to determine water retainability of porous fine aggregate for design and quality control of fresh concrete", *Construction and Building Materials* Vol. 21, No. 6, 2007, pp. 1322-1334.

- [7] Bakharev, T., " Thermal behaviour of geopolymers prepared using class F fly ash and elevated temperature curing", *Cement and Concrete Research* Vol. 36, No. 6, 2006, pp. 1134-1147.
- [8] Gourley, J.T., and G.B. Johnson, "Develoments in geopolymer precast concrete", *World Congress Geopolymer 2005*, Saint-Quentin, France: Institut Géopolymère 2005.
- [9] Palomo, A., M.W. Grutzeck, and M.T. Blanco," Alkali-activated fly ashes: A cement for the future", *Cement and Concrete Research* Vol. 29, No. 8, 1999, pp. 1323-1329.
- [10] Xu, H., and J.S.J. Van Deventer," The geopolymerisation of alumino-silicate minerals", *International Journal of Mineral Processing* Vol. 59, No. 3, 2000, pp. 247-266.
- [11] Chindaprasirt, P., T. Chareerat, and V. Sirivivatnanon," Workability and strength of coarse high calcium fly ash geopolymer", *Cement and Concrete Composites* Vol. 29, No. 3, 2006, pp. 224-229.
- [12] Andrade, L.B., J.C. Rocha, and M. Cheriaf," Influence of coal bottom ash as fine aggregate on fresh properties of concrete", *Construction and Building Materials* Vol. In Press, Corrected Proof, 2008.
- [13] Chindaprasirt, P., C. Jaturapitakkul, W. Chalee, and U. Rattanasak," Comparative study on the characteristics of fly ash and bottom ash geopolymers", *Waste Management* Vol. In Press, Corrected Proof, 2008.
- [14] Álvarez-Ayuso, E., X. Querol, F. Plana, A. Alastuey, N. Moreno, M. Izquierdo, O. Font, T. Moreno, S. Diez, E. Vázquez, and M. Barra," Environmental, physical and structural characterisation of geopolymer matrixes synthesised from coal (co-)combustion fly ashes", *Journal of Hazardous Materials* Vol. In Press, Corrected Proof, 2007, pp. 179.
- [15] Wang, H., H. Li, and F. Yan," Synthesis and mechanical properties of metakaolinite-based geopolymer", *Colloids and Surfaces A: Physicochemical and Engineering Aspects* Vol. 268, No. 1-3, 2005, pp. 1-6.
- [16] Hardjito, D., S.E. Wallah, D.M.J. Sumajouw, and B.V. Rangan," On the Development of Fly Ash-Based Geopolymer Concrete", *ACI Materials Journal* Vol. 101, No. 6, 2004b, pp. 467-472.